



Thermal and Frequency Stability of Dielectric Ceramic $\text{Ba}_{6-3x}\text{Nd}_{8+2x}\text{Ti}_{18}\text{O}_{54}$ ($x=0.15, 0.25$)

Chian Heng Lee^{1*}, Jumiah Hassan^{1,2}, Mansor Hashim²,
Raba'ah Syahidah Aziz^{1,2} and Norlaili Mohd Saiden¹

¹Department of Physics, Universiti Putra Malaysia, 43400 Serdang, Selangor, Malaysia.

²Institute of Advanced Technology, Universiti Putra Malaysia, 43400 Serdang, Selangor, Malaysia.

Authors' contributions

This work was carried out in collaboration between all authors. All authors read and approved the final manuscript.

Article Information

DOI: 10.9734/PSIJ/2014/12908

Editor(s):

(1) Stefano Moretti, School of Physics & Astronomy, University of Southampton, UK.

Reviewers:

(1) Anonymous, Universidade Estadual do Ceará, Brazil.

(2) Manoj Kumar Mishra, Department of Physics, R.R.M. Campus (Tribhuvan University), Janakpur, Nepal.

(3) Anonymous, Al-Nahrain University, Iraq.

Peer review History: <http://www.sciencedomain.org/review-history.php?iid=638&id=33&aid=5951>

Original Research Article

Received 23rd July 2014
Accepted 7th August 2014
Published 6th September 2014

ABSTRACT

A new dielectric material, barium neodymium titanate (BNT) ceramic can provide good thermal and frequency stability on the dielectric properties. The synthesis of BNT ceramics with $x=0.15$ and 0.25 was carried out using wet solid state method. The ceramics were characterized by X-ray diffraction to identify the phase. The shifting of XRD peaks revealed higher content of neodymium ions inside the compound. Surface morphology of the ceramics was determined using FESEM. Different compositions influenced the grain growth of the ceramics. BNT ceramics with higher neodymium content showed higher porosity, and higher resistance to shrinkage. The dielectric properties at low frequency from 40 Hz to 1 MHz were measured using Impedance

*Corresponding author: Email: chianheng16@gmail.com;

Analyzer. The polarization effect inside the material was discussed and compared. BNT ceramics with $x=0.15$ has higher dielectric constant. These BNT ceramics showed frequency and thermal stability with respect to the dielectric constant.

Keywords: Dielectric properties; microstructure; polarization; thermal stability.

1. INTRODUCTION

The dielectric properties of most dielectric ceramics always show temperature and frequency dependence [1-8]. The change in dielectric constant of a ceramic makes it difficult to design the materials for use at a certain temperature. Li et al. [9] studied a dielectric material, BaTiO₃-Na_{0.5}Bi_{0.5}TiO₃-Nb₂O₅-MgO-Glass with Nd₂O₃ addition, and found the capacitance decreases when temperature increases. Su et al. [10] reported the relaxation behaviour of TbCo_{0.5}Mn_{0.5}O_{3.07} ceramics change with increasing temperature. Zaman et al. [11] showed there are two peaks showing temperature dependence of the dielectric constant in the temperature range of 500°C. Adhlakha et al. [12] revealed that hopping of Fe ions is thermally activated in Ni_{0.75}Zn_{0.25}Fe₂O₄ doped with BiFeO₃ composites which affect the dielectric constant. Mocanu et al. [13] reported that Mg_xNi_{1-x}Fe₂O₄ ceramic displays a flattened semicircular arc in complex impedance plot which implies that the electrical properties of that material are frequency dependent. One of the excellent dielectric ceramics is barium titanate, which has a high dielectric constant [14]. However, BaTiO₃ ceramic has a Curie temperature around 125°C [15,16] which points to the changing behavior of ferroelectric to paraelectric. ARAU'JO [17] studied Curie point in barium calcium titanate solid solution and found Curie temperature increases with increasing calcium ions. At this critical temperature, the dielectric constant starts to reduce and influences the properties of the material. In this research, we have synthesized a dielectric material that has good thermal stability and frequency independent dielectric properties. Addition of neodymium ions into barium titanate resulted in the exchange of phase from perovskite to tungsten bronze structure. It has been reported by Korchagina et al. [18] that neodymium has excellent results in low frequency and microwave dielectric properties of Ba₂LnTaO₆ compared to other rare earth elements. Ohsato [19] analyzed the structural properties of tungsten bronze type solid solutions by discussing the lattice parameters and positions of the ions inside the compound. Dielectric ceramic with compositional formula Ba_{6-3x}Nd_{8+2x}Ti₁₈O₅₄, BNT ($x=0.15$) was prepared, and the microstructure and dielectric properties were investigated. In order to understand the important role of diffusion of neodymium ions, another dielectric ceramic BNT with $x=0.25$ was also fabricated and material properties were compared.

2. MATERIALS AND METHODS

The raw materials BaCO₃, Nd₂O₃, and TiO₂ powders with particle size below 100nm were used in this work. All powders were mixed and milled using liquid agent ethanol by magnetic stirring method [11]. The powders were weighed according to the desired composition, and milled for 24 hours. After the milling process, the slurries were dried for another 24 hours. The final dried powders were pressed into pellets with diameter of 17 mm and thickness of 2.8mm. The pellets were pre-sintered at 600°C for 3 hours. The pellets were then sintered for 3 hours in air in a programmable furnace at 1300°C. BNT with $x=0.15$ and 0.25 were prepared in this work. The density of the samples was measured using Archimedes' principle. The structural properties of the ceramics were determined by X-ray diffractometer (Phillips Expert Pro PW3040) with CuK α radiation ($\lambda=1.5404\text{\AA}$). The microstructure of the

ceramics was observed using FESEM. The dielectric properties of the samples were measured using Impedance Analyzer (Agilent Model 4294A) from 40 Hz to 1 MHz at different measuring temperatures, from room temperature to 250°C.

3. RESULTS AND DISCUSSION

The XRD pattern of BNT ceramics with $x=0.15$ and 0.25 at sintering temperature of 1300°C are shown in Fig. 1. It is found that both samples have a tungsten bronze type with orthorhombic structure [19] without any secondary phases, and the patterns were similar. It is clearly shown as Fig. 1 that both ceramics have many sharp peaks located in the 2θ range, and the highest peak was situated around 31 to 32 degrees. Based on the similar pattern of both ceramics, it is necessary to zoom into the highest peak in order to investigate the relationship of the patterns and the compositions. The comparison of XRD peak between the two compositions of BNT ceramics are given in the inset figure of Fig. 1. It can be observed that BNT 0.15 has higher peak intensities than BNT 0.25. The highest peak of BNT sample shows shifting to the higher angle when higher Nd ions were substituted into the system. This indicates that more Nd ions fully incorporated into A1 site of the tungsten bronze type structure which caused distortion in the lattice arrangement. The internal spacing of the arrangement atoms decreases when there are more barium ions replaced by neodymium ions. Interestingly, the shifting behavior of the peak not only shows the change of the structural distortion, but also could be used to predict the dielectric properties of the sample. The BNT ceramic with $x=0.25$ shows the peak shifted to higher 2θ position meaning that the dielectric constant of this sample would be lower than BNT ceramic with $x=0.15$.

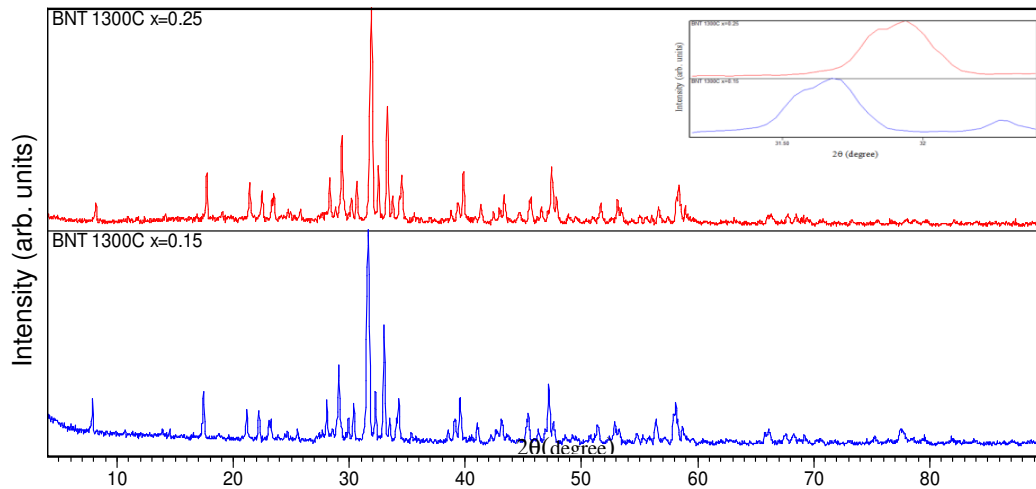


Fig. 1. XRD pattern of BNT ceramic with $x=0.15$ and 0.25 at sintering temperature of 1300°C. Comparison of highest peak of two BNT ceramics (inset figure)

Table 1 shows physical properties of two different compositions of BNT ceramics. The density was obtained using Electronic Densimeter MD300S which adopts Archimedes principle. Shrinkage is taken by calculating the percentage of dimension changed before and after the sintering process. It should be mentioned that BNT with $x=0.25$ shows less shrinkage than the other which implies that there is more neodymium atoms present in the sample. It is stated in atomic properties in the periodic table [20] that the atomic size of

neodymium is bigger than barium atom. Therefore, when there are more barium atoms being replaced by neodymium atoms, the compound has higher resistance to shrinkage. On the other hand, BNT with $x=0.25$ is more porous than BNT with $x=0.15$. It could be related to mass loss during the sintering process. The higher is the mass loss, the smaller is the density. In addition, the increase in porosity might be due to the number of increasing vacancy in the compound. It can be figured out from the structural properties of the compound, if the number of barium atoms decrease in A2 site of a tungsten bronze structure [21], then it will create a space. This space could not fill by larger size atoms such as neodymium atom, which made this ceramic becomes less dense.

Table 1. Physical properties of BNT ceramics

Compositions	Density (g cm^{-3})	Shrinkage (%)	Mass loss (%)	Average grain size (μm)
$x=0.15$	4.57	43.59	3.96	0.754
$x=0.25$	3.60	39.73	4.90	0.586

Comparison of surface morphology between different compositions of BNT ceramics is revealed in Fig. 2. The estimated grain size was analyzed using linear intercept method by choosing 200 grains inside the sample. The results show that BNT ceramic with $x=0.15$ has bigger grain size than BNT ceramic with $x=0.25$. Both BNT ceramics have fully achieved densification where the grains and grain boundaries can be differentiated clearly on the surface. In view of the grain shape, BNT ceramic with $x=0.25$ did not shows much rectangular grain shape as BNT ceramic with $x=0.15$. Not only that, BNT ceramic with $x=0.25$ displays more porosity on the surface where there is more dark area that was observed in Fig. 3 (b). This porous effect can also be confirmed by the measured density, which reveals the sample has lower density. It could be noticed that, BNT ceramic with more neodymium ions blocked the formation of longer grain shape. The porosity of this sample influenced the dielectric properties of the material. The space between the grains made the material loses the ability to store charges. This was exhibited in the dielectric results, which shows the higher neodymium content has lower dielectric constant.

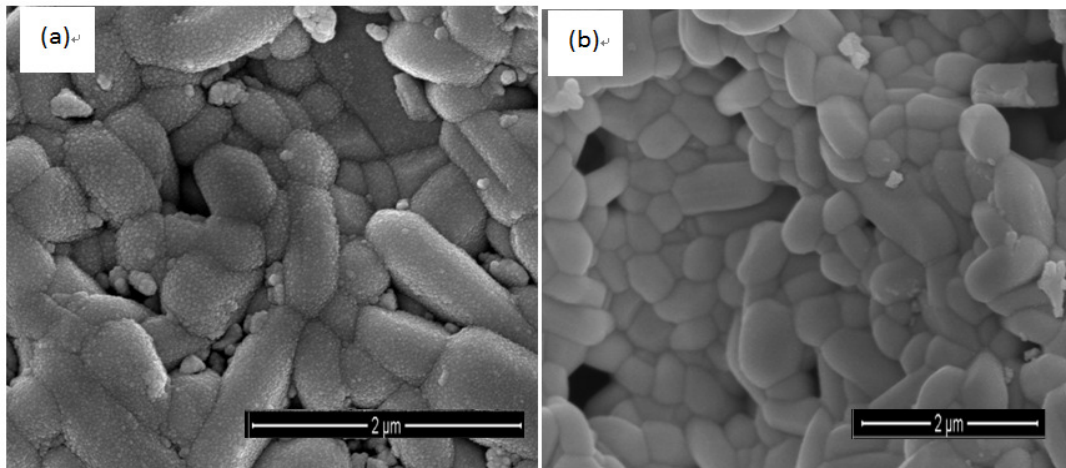


Fig. 2. Microstructure of BNT ceramic sintered at 1300°C ; (a) BNT $x=0.15$ and (b) BNT $x=0.25$

Fig. 3 shows the dielectric properties as a function of frequency for BNT ceramics with $x=0.15$ and 0.25 at room temperature and 250°C . The results revealed that the dielectric constant of both ceramics is independent of frequency from 40 Hz to 1 MHz . This property is against the common behaviour of materials which normally showed the dielectric constant decreases with increasing frequency [22-25]. The good frequency stability of these ceramics is normally related to structure of the materials itself. The tungsten bronze type structure always leads the dielectric constant of the material to behave independently of frequency. As can be observed from the results, the Maxwell Wagner type of interfacial polarization [26-28] does not occur in this type of material. In most materials, the dielectric constant is always increased by this polarization effect, especially in the low frequency region. However, the interfacial polarization was eliminated by these two BNT ceramics. This also indicates that there is only orientation polarization [29] occurring in this material. The imaginary part of the dielectric constant or loss factor [30,31] as a function of frequency for BNT ceramics with $x=0.15$ and 0.25 is shown in Fig. 4. The dielectric loss factor shows a decrease with respect to frequency for both BNT ceramics at all measuring temperatures. No peak can be seen from the results. Therefore, the relaxation of the ceramics could not be defined in this frequency range. The decrement of dielectric loss factor indicates the lossy behaviour of the material can be improved by selecting the correct frequency. On the other hand, when different temperatures were applied to these ceramics, the dielectric loss factor showed no effect at low frequency region. However, loss factor shows a slight increase at high frequency region as temperature increases. This will give an impact to quality factor of the materials. The comparison of dielectric constant as a function of measuring temperature at selected frequency of 1 MHz is given in Fig. 4. The results show that, BNT ceramic with $x=0.15$ has higher dielectric constant. This can be related to several factors. One of the reasons might be related to the shifting behaviour of the highest peak of the ceramics. Besides, the BNT ceramic with $x=0.25$ shows more porosity. On the other hand, both BNT ceramics have good thermal stability in the dielectric constant with the applied measuring temperature. This means that the dipole moment inside the material is already aligned and the poling field did not influenced much on the dipole motions. The dielectric constant showed not much difference indicating these materials can be used in high temperature applications.

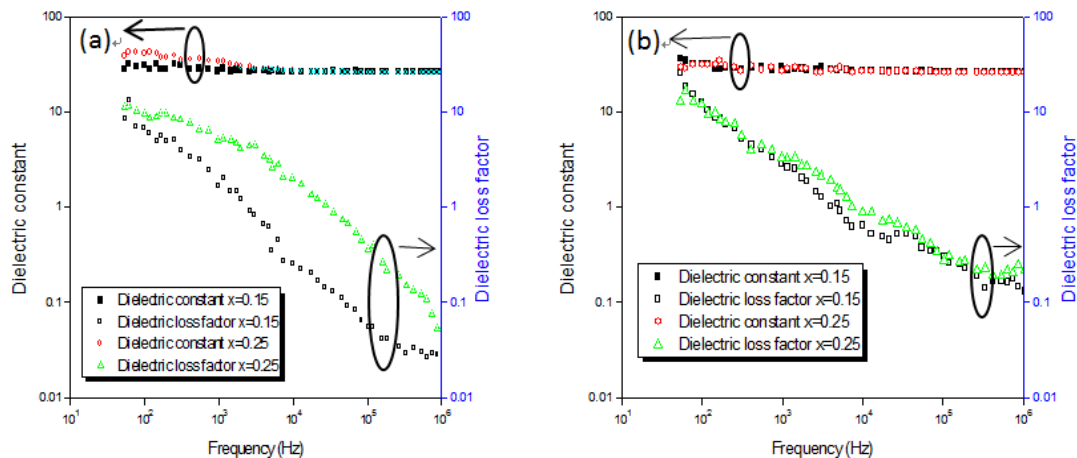


Fig. 3. Dielectric constant and loss factor as a function of frequency: (a) room temperature, (b) 250°C

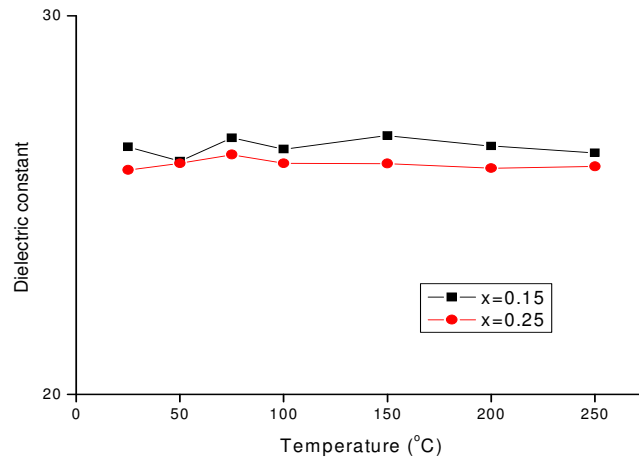


Fig. 4. Dielectric constant as a function of measuring temperature for BNT 0.15 and BNT 0.25 exhibiting thermal stability

4. CONCLUSION

In conclusion, BNT ceramics with different compositions were fabricated. The shifting of XRD pattern indicates the changing in the interplanar spacing of the compound. BNT ceramic with higher neodymium ions content has higher porosity, and smaller grain size. The dielectric properties show stability in frequency and temperature for both BNT ceramics. Increasing of neodymium ions led to the decrease in the dielectric constant in the tungsten bronze structure. Due to the frequency independence of the dielectric constant, these types of materials can also be used in microwave technology and telecommunication system.

ACKNOWLEDGEMENTS

This research was financially supported from the Research University Grant Scheme (RUGS) Project No.: 05-02-12-2180RU, Universiti Putra Malaysia (UPM). The authors also acknowledged the Department of Physics, Faculty of Science, UPM and Institute of Advanced Technology (ITMA), UPM.

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

1. Wang JY, Zhang XY, Zhang JJ, Li HL, Li ZF. Dielectric and Piezoelectric Properties of $(1-x)\text{Ba}_{0.7}\text{Sr}_{0.3}\text{TiO}_3-x\text{Ba}_{0.7}\text{Ca}_{0.3}\text{TiO}_3$ Perovskites. *Journal of Physics and Chemistry of Solids*. 2012;73(7):957-960.
2. Kumar Patel P, Rani J, Adhlakha N, Singh H, Yadav KL. Enhanced dielectric properties of doped barium titanate ceramics. *Journal of Physics and Chemistry of Solids*. 2013;74.4:545-549.

3. Lin D, Huang D, Zhang QJ. Structure, dielectric and piezoelectric properties of $K_{0.5}Na_{0.5}NbO_3-Bi_{0.5}(Na_{0.7}K_{0.2}Li_{0.1})_{0.5}TiO_3$ Ceramics. *Journal of Physics and Chemistry of Solids*. 2013;74(7):1021-1025.
4. Kar SK and Kumar P. Structural, morphological and dielectric study of $Ba(FeNb)_{0.5}O_3$ ceramics synthesized by microwave processing technique. *Journal of Physics and Chemistry of Solids*. 2013;74(10):1408-1413.
5. Sun ZX, Pu YP, Dong ZJ, Hu Y, Wang PK, Liu XY, Wang Z. Impact of fast microwave sintering on the grain growth, dielectric relaxation and piezoelectric properties on $Ba_{0.18}Ca_{0.02}Ti_{0.09}Zr_{0.10}O_3$ Lead-Free Ceramics Prepared by Different Methods. *Materials Science and Engineering: B*. 2014;185.0:114-1122.
6. Madhu BJ, Ashwini ST, Shruthi B, Divyashree BS, Manjunath A, Jayanna HS. Structural, dielectric and electromagnetic shielding properties of Ni-Cu nanoferrite/PVP Composites. *Materials Science and Engineering: B*. 2014;186.0:1-6.
7. Mandal SK, Dey P, Nath TK. Structural, Electrical and dielectric properties of $La_{0.7}Sr_{0.3}MnO_3-ErMnO_3$ Multiferroic Composites. *Materials Science and Engineering: B*. 2014;181(0):70-76.
8. Varalaxmi N, Sivakumar KV. Structural and Dielectric Studies of Magnesium Substituted NiCuZn Ferrites for Microinductor Applications. *Materials Science and Engineering: B*. 2014;184(0):88-97.
9. Li LX, Guo D, Xia WS, Liao QW, Han YM, Peng Y. An ultra-broad working temperature dielectric material of $BaTiO_3$ -based ceramics with Nd_2O_3 addition. *Journal of the American Ceramic Society*. 2012;95(7):2107-2109.
10. Su J, Zhang JT, Lu XM, Lu CJ, He J, Li QC, Zhu JS. Magnetic and dielectric properties of Metamagnetic $TbCo_{0.5}Mn_{0.5}O_{3.07}$ Ceramics. *Journal of Materials Science*. 2014;49.10:3681-3686.
11. Zaman A, Iqbal Y, Hussain A, Kim MH, Malik RA. Dielectric, ferroelectric, and field-induced strain properties of Ta-doped $0.99Bi_{0.5}(Na_{0.82}K_{0.18})_{0.5}TiO_3-0.01LiSbO_3$ Ceramics. *Journal of Materials Science*. 2014;49.8:3205-3214.
12. Adhlakha N, Yadav KL. Structural, dielectric, magnetic, and optical properties of $Ni_{0.75}Zn_{0.25}Fe_2O_4-BiFeO_3$ Composites. *Journal of Materials Science*. 2014;49(13):4423-4438.
13. Mocanu ZV, Airimioaei M, Ciomaga CE, Curecheriu L, Tudorache F, Tascu S, Iordan AR, Palamaru NM, Mitoseriu L. Investigation of the functional properties of $MgxNi_{1-x}Fe_2O_4$ Ceramics. *Journal of Materials Science*. 2014;49(8):3276-86.
14. Ctibor P, Seiner H, Sedlacek J, Pala Z, Vanek P. Phase stabilization in plasma sprayed $BaTiO_3$. *Ceramic International*. 2013;39(5):5039-5048
15. Badheka P, Qi L, Lee B. Phase transition in barium titanate nanocrystals by chemical treatment. *Journal of the European Ceramic Society*. 2006;26(8):1393-1400
16. Pornprasertsuk R, Yuwapattanawong C, Permkittikul S, ungtidtham T. Preparation of doped $BaZrO_3$ and $BaCeO_3$ from nanopowders. *International Journal of Precision Engineering and Manufacturing*. 2012;13(10):1813-1819.
17. Araujo VD, Motta FV, Marques APA, Paskocimas CA, Bomio MRD, Longo E, Varela JA. Effect of calcium on the structural properties of $Ba_{(1-x)}Ca_xTiO_3$ particles synthesized by complex polymerization method. *Journal of Materials Science*. 2014;49.7: 2875-2878.
18. Korchagina SK, Shevchuk YA. Low-frequency and microwave dielectric properties of Ba_2LnTaO_6 ($Ln=La, pr, sm, dy, ce, gd, nd, tm, tb$) ceramics. *Inorganic Material*. 2006;42(1):64-67.
19. Ohsato H. Science of tungstenbronze-type like $Ba_{6-3x}R_{8+2x}Ti_{18}O_{54}$ ($R=rare\ Earth$) microwave dielectric solid solutions. *Journal of the European Ceramic Society*. 2001;21(15): 2703-2711.

20. David R. Lide, ed. CRC Handbook of Chemistry and Physics, 90th Edition (CD-ROM Version), CRC Press, Taylor and Francis, Boca Raton, FL; 2010.
21. Chen YC, Huang CL. Microwave dielectric properties of Ba_{2-x}Sm_{4+2/3x}Ti₉O₂₆ ceramics with zero temperature coefficient. Materials Science and Engineering A334 2002;250–256.
22. Yan M, Tan YQ, Zhao H, Peng J, Xiao XL, Hu ZB. Crystal structure, dielectric and magnetic properties of Ba₅NdNi_{1.5}Nb_{8.5}O₃₀ tungsten bronze ceramic. Materials Chemistry and Physics. 2012;136.2:487-491.
23. Fang, L, Xiang F, Liao W, Liu LJ, Zhang H, Kuang XJ. Dielectric properties and high-temperature dielectric relaxation of Ba₃Ti₄Nb₄O₂₁ ceramic. Materials Chemistry and Physics. 2014;143(2):552-556.
24. Chen JW, Narsinga Rao G, Lee HM, Lee WL, Chou FC. Dielectric properties of the Spin-1/2 Dimer compounds Ba₃Cr₂O₈ and Sr₃Cr₂O₈. Materials Chemistry and Physics. 2014;145(3):461-464.
25. Cao WQ, Chen W. Dielectric Properties of Y₂O₃ Donor-Doped Ba_{0.8}Sr_{0.2}TiO₃ Ceramics. Materials Chemistry and Physics. 2014;143(2):676-680.
26. Samkaria R, Sharma V. Effect of Rare Earth Yttrium Substitution on the Structural, Dielectric and Electrical Properties of Nanosized Nickel Aluminate. Materials Science and Engineering: B. 2013;178.20:1410-1415.
27. Maxwell JC. A treatise on electricity and magnetism, vol. 2, Dover Publications: Oxford, NY; 1954.
28. Koops CG. Phys. Rev. 1951;83:121–124.
29. Raju GG. Polarization and static dielectric constant. Dielectrics in Electric Fields. CRC Press: 2003.
30. Raju GG. Dielectric loss and relaxation - I. Dielectrics in Electric Fields. CRC Press; 2003.
31. Raju GG. Dielectric loss and relaxation - II. Dielectrics in Electric Fields. CRC Press; 2003.

© 2014 Lee et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/3.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:
<http://www.sciencedomain.org/review-history.php?iid=638&id=33&aid=5951>